



Cite this: *Chem. Commun.*, 2016, 52, 9371

Received 24th June 2016,
Accepted 27th June 2016

DOI: 10.1039/c6cc05222c

www.rsc.org/chemcomm

Peripheral ligands as electron storage reservoirs and their role in enhancement of photocatalytic hydrogen generation†

Qing Pan,^a Leon Freitag,^b Tanja Kowacs,^c Jane C. Falgenhauer,^d Jeroen P. Kortarik,^a Derck Schlettwein,^d Wesley R. Browne,^e Mary T. Pryce,^f Sven Rau,^c Leticia González,^{*b} Johannes G. Vos^{*f} and Annemarie Huijser^{*a}

The contrasting early-time photodynamics of two related Ru/Pt photocatalysts with very different photocatalytic H₂ generation capabilities are reported. Ultrafast equilibration (535 ± 17 fs) creates an electron reservoir on the peripheral ligands of the ester substituted complex, allowing a dramatic increase in photocatalytic performance. This insight opens the way towards a novel design strategy for H₂ generating molecular photocatalysts.

Hydrogen generating molecular photocatalysts that mimic natural photosynthesis have been studied intensively in recent years.¹ Since the first reports on H₂ evolving Ru/M (M = Pt or Pd) bimetallic photocatalysts independently published by Sakai and Rau in 2006,² many efforts have been made to increase the H₂ generation efficiency in terms of both the turn-over number (TON) and turn-over frequency (TOF).³ Such optimisation studies are, however, complex since the photocatalytic efficiency is the result of a sequence of photophysical and photochemical processes occurring in a broad window of time scales. A sacrificial agent such as triethylamine (TEA) is required to regenerate the photosensitiser by electron donation to the formally oxidised Ru(III) centre. This process however also results in the formation of radicals, which may lead to side reactions by reacting with solvents (Section S5, ESI†). The presence of TEA, thus, prevents photophysical studies under catalytic conditions. However, earlier studies showed that

the early-time (fs–ns) photodynamics under non-catalytic conditions provide important mechanistic insight into the photocatalytic performance. For instance, it was concluded that the electron density distribution of the initial photoexcited state determines the H₂ generation efficiency.⁴ Furthermore, the occurrence of intramolecular electron transfer in the ps time window was shown to be essential.⁵ Hence, understanding of the fundamental early-time photodynamics is an important first step towards the design of improved photocatalysts. Such knowledge also facilitates the investigation of subsequent processes occurring at later time scales. This communication will therefore focus on the early-time photodynamics.

The early-time photodynamics and photocatalytic efficiency have been shown to be dependent on the peripheral/bridging ligands and the catalytic centre.⁶ Resonance Raman studies on various Ru/Pt and Ru/Pd complexes indicate that photoexcitation leads to the population of singlet ¹MLCT (metal-to-ligand charge transfer) states based on both the peripheral and bridging ligands.^{5a,b,6a} The intertwined involvement of these components suggests the importance of dynamic communication between different functional groups especially in the excited states. For instance, inter-ligand electron transfer has been observed in **RuPd** (Fig. 1) on a ps time scale, competing with vibrational cooling of excited states localised on the peripheral ligands,

^a MESA + Institute for Nanotechnology, University of Twente, P.O. Box 217, 7500 AE, Enschede, The Netherlands. E-mail: j.m.huijser@utwente.nl

^b Institute of Theoretical Chemistry, University of Vienna, Währinger Str. 17, 1090 Vienna, Austria. E-mail: leticia.gonzalez@univie.ac.at

^c Institute of Inorganic Chemistry Materials and Catalysis, University of Ulm, Albert-Einstein-Allee 11, 89081 Ulm, Germany

^d Institute of Applied Physics, Justus-Liebig-University, Ludwigstraße 23, 35390 Gießen, Germany

^e Stratingh Institute for Chemistry, University of Groningen, 9747 AG, Groningen, The Netherlands

^f SRC for Solar Energy Conversion, School of Chemical Sciences, Dublin City University, Glasnevin, Dublin 9, Ireland. E-mail: han.vos@dcu.ie

† Electronic supplementary information (ESI) available: Experimental methods, additional spectroscopy and DFT results. See DOI: 10.1039/c6cc05222c



Fig. 1 Structure of the photocatalysts **RuPd**, **RuPt** and **EtOOCRuPt**. The ester unsubstituted and substituted precursors are denoted as **Ru** and **EtOOCRu**, respectively. S = solvent (acetonitrile). See Section S3, ESI† for more details.

limiting the charge transfer efficiency towards the bridging ligand.^{5a} Functionalising the bridging ligand of a Ru/Pt photocatalyst with an electron withdrawing CN group was observed to accelerate electron transfer to the bridging ligand and the H₂ generation rate.^{5c} Based on these observations, it is commonly accepted that a favouring population of excited states localised on the bridging ligand is essential for efficient photocatalysis. Generally the bridging ligand is designed to facilitate electron transfer from the photosensitiser to the catalytic centre, and store the photogenerated electron prior to any subsequent photochemical reactions.^{4,6d} However, a recent study shows that an additional charge localised on the bridging ligand of an electrochemically mono-reduced Ru/Pt catalyst prevents directional transfer of the second electron.⁷ Utilisation of triplet ³MLCT states localised on the peripheral ligands is envisioned to be a pathway to increasing the efficiency of the essential second electron transfer process.

Indeed, comparison of a series of Ru/Pt and Ru/Pd complexes raises several questions. Two closely related bimetallic assemblies based on the same di(pyridine-2-yl)pyrazine (2,5-dpp) bridging ligand are both inactive in photocatalytic hydrogen generation,^{3a,6b} suggesting that 2,5-dpp is not a suitable bridging ligand. Remarkably, functionalisation with ester groups of the peripheral 2,2'-bipyridine (bpy) ligands leads to a complex showing a TON of 400.^{6b} A similar effect was also observed for 2,3-dpp bridged complexes.^{6a,8} More recently, two related Ru/Pt complexes based on a 2,2':5',2''-terpyridine (tpy) bridging ligand have been investigated by our groups (**RuPt** and **EtOOCRuPt**, Fig. 1). **EtOOCRuPt** shows a significantly improved performance (TON = 650 after 6 h of irradiation at 470 nm) as compared to **RuPt** (TON = 80) in the same reaction conditions.⁹ For **RuPd**, a TON of 120 was reported.^{6c} Although hydrogen generation depends on other parameters as well, it becomes clear that the peripheral ligands play a central role. To the best of our knowledge, no photodynamical investigation has been reported to explain the beneficial effect of ester functionalised peripheral ligands of these complexes.

Intersystem crossing (ISC) to the triplet manifold in Ru(II)-polypyridyl complexes is known to occur within 100 fs after photoexcitation¹⁰ and hence it is the energetics of the triplet states that determine the early-time photodynamics. The geometries and spin density distribution at the minima of the lowest ³MLCT states (Fig. 2) calculated by density functional theory (DFT), indicate that the order of the ³MLCT states changes upon ester modification of the peripheral ligands (Table S3-2, ESI[†]). For **Ru** and **RuPt**, a tpy-based ³MLCT state is the lowest in energy, whereas for **EtOOCRu** and **EtOOCRuPt** an EtOOC-bpy-based state becomes the lowest. This trend is the same for the lowest unoccupied molecular orbitals calculated at the ground state geometry (Fig. S3-1, ESI[†]).

The time evolution of the population of the (EtOOC-)bpy and tpy-localised ³MLCT states of **Ru** and **EtOOCRu** has been studied by transient absorption (TA). Fig. 3 (and Fig. S4-1, ESI[†]) shows the TA spectra of **Ru** and **EtOOCRu**. The TA spectrum of **Ru** shows two bands around 370 nm and 420 nm, with the first due to excited state absorption (ESA) of the bpy radical anion and the second related to the tpy radical anion.^{5a,11} The ESA

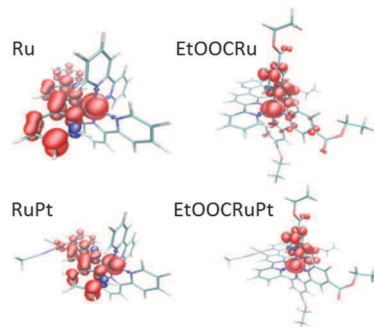


Fig. 2 Spin densities of the lowest triplet states of **Ru**, **EtOOCRu**, **RuPt** and **EtOOCRuPt** in acetonitrile.

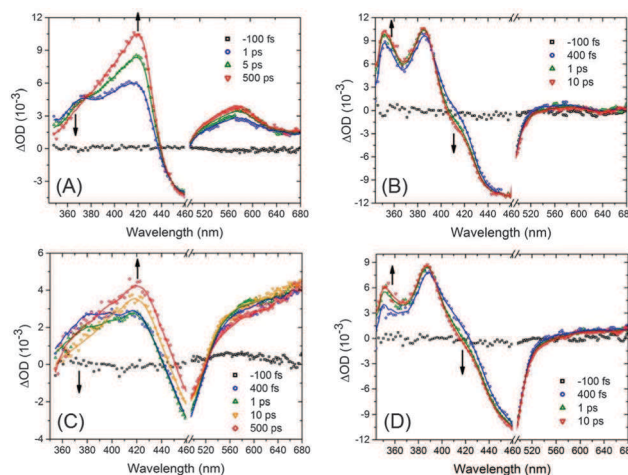


Fig. 3 TA spectra of **Ru** (A), **EtOOCRu** (B), **RuPt** (C) and **EtOOCRuPt** (D) in anhydrous acetonitrile, including fits presented as solid curves.†

increase around 420 nm concomitant with a decrease at *ca.* 370 nm in time manifests internal conversion (IC) from a bpy-based to a tpy-based ³MLCT state occurring within *ca.* 20 ps. Vibrational cooling is likely competing with this process.^{5a}

The TA spectral features observed for **EtOOCRu** are different from those of **Ru**. An ESA band at *ca.* 350 nm increases in intensity within 1 ps, concomitant with a decrease of ESA at *ca.* 420 nm, as also evident from the kinetic traces provided in Fig. S4-1B (ESI[†]). Since the DFT calculations show that the ³MLCT_{EtOOC-bpy} state is lower in energy than the ³MLCT_{tpy} state, the observed dynamics likely reflect ³MLCT_{tpy} → ³MLCT_{EtOOC-bpy} IC. Based on this interpretation, the ESA bands at *ca.* 350 nm and 420 nm are assigned to the reduced EtOOC-bpy and tpy ligands, respectively. An additional ESA band is present at *ca.* 385 nm, which does not evolve in time significantly, likely due to the overlapping contributions from the nearby ESA bands around 350 nm and 420 nm. The observation of a similar band at *ca.* 385 nm for the homoleptic complex [Ru(EtOOC-bpy)₃]²⁺ in acetonitrile¹² indicates that this ESA band is likely associated to a reduced EtOOC-bpy ligand. The assignment of the ESA bands at both 350 nm and 385 nm to the EtOOC-bpy ligands is consistent with the species associated spectra (Fig. S4-3, ESI[†]) obtained from the photophysical model shown in Fig. S4-2 (ESI[†]). Further indirect

support is provided by the differential absorption spectra under electrochemical reduction conditions (Fig. S2-3, ESI[†]). The above assignment suggests that, although ester functionalisation of the bpy ligands does not significantly alter the ESA position of the tpy ligand at *ca.* 420 nm, the bpy-based ESA band is split, possibly due to coupling between different ligands.[§] The absence of spectral changes at times beyond a few ps (up to at least 6 ns, Fig. S4-4, ESI[†]) indicates that the formed ³MLCT manifold is long-lived and excited state equilibration between ³MLCT_{EtOOC-bpy} and ³MLCT_{tpy} states in **EtOOCRu** is ultrafast (Fig. S4-2, ESI[†]).

The TA spectral features of **RuPt** and **EtOOCRuPt** (Fig. 3) are similar to those of their mononuclear precursors. For **RuPt**, an ESA band at *ca.* 370 nm becomes less intense in time concomitant with a growth of an ESA at *ca.* 420 nm, indicating IC from bpy-localised ³MLCT states to tpy-based ³MLCT states. Again, as observed for the two monometallic precursors, the direction of IC observed for **EtOOCRuPt** is opposite to that of **RuPt**, indicating that cyclometalation by Pt does not change the direction of ultrafast intramolecular electron transfer.

A photophysical model of **EtOOCRuPt** established by target analysis of the TA data is shown in Fig. 4. The obtained species associated spectra are provided in Fig. S4-5 (ESI[†]). Photoexcitation leads to EtOOC-bpy and tpy-based singlet excited states, which undergo ultrafast ISC¹⁰ into EtOOC-bpy and tpy-Pt localised triplet states. The electron density at the bridge side moves on an ultrafast timescale to the EtOOC-bpy ligands (535 ± 17 fs). The backward electron transfer from EtOOC-bpy to tpy-Pt occurs at >3 ps. This equilibration results in only a minor population of the bridge based states.

The TA data discussed above allow interpretation of the time-resolved photoluminescence data obtained before.⁹ The excited state decay of **Ru** is mono-exponential ($\tau = 796 \pm 6$ ns), indicating that the various peripheral and bridging ligand based low lying ³MLCT states are thermally equilibrated.¹³ For **EtOOCRu** ($\tau = 1.05 \pm 0.01$ μ s) and **EtOOCRuPt** ($\tau = 625 \pm 31$ ns), ultrafast excited state equilibration results in a major population of the ³MLCT_{EtOOC-bpy} states, yielding a mono-exponential emission decay. However, for **RuPt** a bi-exponential decay ($\tau_1 = 124 \pm 58$ ns, 15%; $\tau_2 = 658 \pm 19$ ns, 85%) is observed. **RuPd** shows analogous features with the fast component more pronounced.^{5a} The fast component observed for **RuPt** is possibly due to enhanced spin-orbit coupling caused by Pt increasing the radiative decay rate. Alternatively, it can be

explained by an increased rigidity of the bridging ligand upon coordination with the Pt centre, possibly resulting in a lowering of the energy of the deactivating triplet metal-centred (³MC) level at the Ru moiety. The increased rigidity may also reduce the vibrational freedom of the ligand thereby increasing the difficulty of inter-ligand IC. This hypothesis is in agreement with DFT calculations showing that the root-mean-square deviation between the bpy and tpy structures increases upon bonding of the Pt centre (Table S3-2, ESI[†]). As a result, both ³MLCT states contribute to the photoluminescence, resulting in a bi-exponential decay.

As discussed above, an important effect of ester functionalisation of the peripheral bpy ligands involves a lowering in ³MLCT energy levels. A major consequence is an inversion in inter-ligand IC direction, causing an ultrafast (535 ± 17 fs) population of ³MLCT states localised on the peripheral ligands. This result seemingly indicates that electron density is moving in a disadvantageous direction. *A priori*, it could be anticipated that movement of electron density from the photosensitiser to the catalytic centre by population of the bridging ligand would be beneficial for photocatalytic H⁺ reduction. This strategy has been applied before by substitution of the bridge with an electron withdrawing CN group in a Ru/Pt photocatalyst (**RuPt-CN**), and improved electron transfer to the catalytic Pt moiety and hydrogen evolution were observed.^{5c} However, for **EtOOCRuPt** the electron transfer direction is the opposite while at the same time a much higher efficiency is achieved for **EtOOCRuPt** compared to **RuPt**.⁹ Definitely, the present work provides the first photophysical evidence challenging the conventional design paradigm based on a bridging ligand acting as electron density storage reservoir.

Establishing a connection between storage of electron density at the peripheral ligands at early-times and the high H₂ TON and TOF values is not straightforward considering the multiple photochemical reactions occurring at later times. However, it is important to consider two key parameters required for efficient H₂ generation; a long excited state lifetime and efficient IC towards the bridging ligand. A long excited state lifetime is essential to allow multiple slow (diffusion controlled) processes to proceed. However, fast IC to the bridge does not guarantee a long lifetime. For instance, a negative side effect observed in **RuPt-CN** involved the recombination of 30–40% of the excited states within ~1 ps.^{5c} Deactivation induced by the cyclometalated Pt due to, *e.g.* strong spin-orbit coupling and additional nonradiative deactivation, is likely to reduce the bridge-based excited state lifetime.^{5a} However, when the photoexcited electron is localised on the peripheral ligands, the relatively longer distance to the Pt centre makes the Pt induced deactivation channels less accessible. Furthermore, functionalisation of the peripheral ligands with ester groups stabilises the ³MLCT states, increasing the gap with the deactivating ³MC state.¹⁴ These effects result in a longer excited state lifetime. An analogous trend has been observed in Ru/Mn photocatalysts for oxygen evolution: the lifetime is reduced from 1400 ns to 23 ns upon Mn coupling for unsubstituted complexes, whereas for the ester substituted analogues the lifetimes remain almost independent of Mn coupling (>1000 ns).¹⁵ Most interestingly, when the ester group is also present at the bridge, the

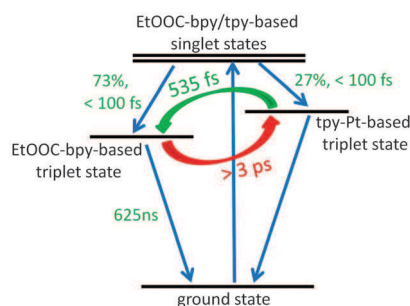


Fig. 4 Simplified photophysical model of light-induced processes in **EtOOCRuPt**.

improvement achieved by ester functionalisation of the peripheral ligands is lost.¹⁶ Besides an improved excited state lifetime, populating the peripheral ligands by the first photogenerated electron may also have a significant impact on the potential energy surfaces relevant for the second photoelectron, promoting future investigation of this fundamental aspect.

In summary, the key observation in the present work is that ultrafast intramolecular equilibration resulting in storing the first photogenerated electron on the peripheral ligands at early times allows a considerable increase in photocatalytic efficiency. This observation cannot be explained within the traditional framework based on the bridging ligand acting as electron storage reservoir. An important advantage of ³MLCT states on the peripheral ligands relative to those on the bridge is their lower susceptibility to excited state deactivation induced by the catalytic centre. These results allow for the development of new design futures for the optimisation of molecular photocatalysts.

This work is supported by the Dutch Organisation for Scientific Research (NWO) and the EU-COST Action PERSPECT-H₂O (STSM 16737). Glotaran¹⁷ was used for data analysis. Prof. Huib Bakker (AMOLF) is acknowledged for discussions.

Notes and references

‡ The fits for EtOOCRu and EtOOCRuPt are based on the photophysical models shown in Fig. S4-2 (ESI[†]) and Fig. 4. The fits for Ru and RuPt are obtained from global analysis using a sequential model.^{6g}

§ The ESA features of related heteroleptic complexes are known to depend on the combination of ligands. An ESA band at ca. 350 nm was found for [Ru(EtOOC-bpy)₂BTL]²⁺ (BTL = 9'-[4,5-bis(cyanoethylthio)]-[1,3-dithiol-2-ylidene]-4',5'-diazafuorene).¹⁸ For [Ru(EtOOC-bpy)₂(2,3-dpp)Pt]²⁺, an ESA band at ca. 385 nm was observed,^{6a} while [Ru(EtOOC-bpy)(bpy)₂]²⁺ manifests a broad ESA band below ca. 400 nm.¹⁹

- (a) L. C. Sun, L. Hammarström, B. Akermark and S. Styring, *Chem. Soc. Rev.*, 2001, **30**, 36; (b) A. Magnuson, M. Anderlund, O. Johansson, P. Lindblad, R. Lomoth, T. Polivka, S. Ott, K. Stensjo, S. Styring, V. Sundström and L. Hammarström, *Acc. Chem. Res.*, 2009, **42**, 1899; (c) L. Hammarström, *Acc. Chem. Res.*, 2015, **48**, 840.
- (a) H. Ozawa, M. A. Haga and K. Sakai, *J. Am. Chem. Soc.*, 2006, **128**, 4926; (b) S. Rau, B. Schafer, D. Gleich, E. Anders, M. Rudolph, M. Friedrich, H. Gork, W. Henry and J. G. Vos, *Angew. Chem., Int. Ed.*, 2006, **45**, 6215.
- (a) H. Ozawa and K. Sakai, *Chem. Commun.*, 2011, **47**, 2227; (b) Y. Halpin, M. T. Pryce, S. Rau, D. Dini and J. G. Vos, *Dalton Trans.*, 2013, **42**, 16243.
- S. Tschierlei, M. Karnahl, M. Presselt, B. Dietzek, J. Guthmuller, L. Gonzalez, M. Schmitt, S. Rau and J. Popp, *Angew. Chem., Int. Ed.*, 2010, **49**, 3981.
- (a) Q. Pan, F. Mecozzi, J. P. Korterik, D. Sharma, J. L. Herek, J. G. Vos, W. R. Browne and A. Huijser, *J. Phys. Chem. C*, 2014, **118**, 20799; (b) S. Tschierlei, M. Presselt, C. Kuhnt, A. Yartsev, T. Pascher, V. Sundström, M. Karnahl, M. Schwalbe, B. Schafer, S. Rau, M. Schmitt, B. Dietzek and J. Popp, *Chem. – Eur. J.*, 2009, **15**, 7678; (c) C. V. Suneesh, B. Balan, H. Ozawa, Y. Nakamura, T. Katayama, M. Muramatsu, Y. Nagasawa, H. Miyasaka and K. Sakai, *Phys. Chem. Chem. Phys.*, 2014, **16**, 1607.
- (a) T. Kowacs, Q. Pan, P. Lang, L. O'Reilly, S. Rau, W. R. Browne, M. T. Pryce, A. Huijser and J. G. Vos, *Faraday Discuss.*, 2015, **185**, 143; (b) G. S. Bindra, M. Schulz, A. Paul, S. Soman, R. Groarke, J. Inglis, M. T. Pryce, W. R. Browne, S. Rau, B. J. Maclean and J. G. Vos, *Dalton Trans.*, 2011, **40**, 10812; (c) G. S. Bindra, M. Schulz, A. Paul, R. Groarke, S. Soman, J. L. Inglis, W. R. Browne, M. G. Pfeffer, S. Rau, B. J. MacLean, M. T. Pryce and J. G. Vos, *Dalton Trans.*, 2012, **41**, 13050; (d) M. Karnahl, C. Kuhnt, F. Ma, A. Yartsev, M. Schmitt, B. Dietzek, S. Rau and J. Popp, *ChemPhysChem*, 2011, **12**, 2101; (e) M. G. Pfeffer, B. Schafer, G. Smolentsev, J. Uhlig, N. Nazarenko, J. Guthmuller, C. Kuhnt, M. Wachtler, B. Dietzek, V. Sundström and S. Rau, *Angew. Chem., Int. Ed.*, 2015, **54**, 5044; (f) M. G. Pfeffer, T. Kowacs, M. Wachtler, J. Guthmuller, B. Dietzek, J. G. Vos and S. Rau, *Angew. Chem., Int. Ed.*, 2015, **54**, 6627; (g) Q. Pan, F. Mecozzi, J. P. Korterik, J. G. Vos, W. R. Browne and A. Huijser, *ChemPhysChem*, 2016, DOI: 10.1002/cphc.201600458.
- L. Zedler, J. Guthmuller, I. R. de Moraes, S. Kupfer, S. Kriech, M. Schmitt, J. Popp, S. Rau and B. Dietzek, *Chem. Commun.*, 2014, **50**, 5227.
- H. Ozawa, Y. Yokoyama, M. Haga and K. Sakai, *Dalton Trans.*, 2007, 1197.
- T. Kowacs, L. O'Reilly, Q. Pan, A. Huijser, P. Lang, S. Rau, W. R. Browne, M. T. Pryce and J. G. Vos, *Inorg. Chem.*, 2016, **55**, 2685.
- (a) N. H. Damrauer, G. Cerullo, A. Yeh, T. R. Bousie, C. V. Shank and J. K. McCusker, *Science*, 1997, **275**, 54; (b) A. Cannizzo, F. van Mourik, W. Gawelda, G. Zgrablic, C. Bressler and M. Chergui, *Angew. Chem., Int. Ed.*, 2006, **45**, 3174.
- (a) S. Wallin, J. Davidsson, J. Modin and L. Hammarstrom, *J. Phys. Chem. A*, 2005, **109**, 4697; (b) C. W. Stark, W. J. Schreier, J. Lucon, E. Edwards, T. Douglas and B. Kohler, *J. Phys. Chem. A*, 2015, **119**, 4813.
- B. H. Farnum, J. M. Gardner and G. J. Meyer, *Inorg. Chem.*, 2010, **49**, 10223.
- D. Magde, M. D. Magde and E. C. Glazer, *Coord. Chem. Rev.*, 2016, **306**, 447.
- M. Maestri, N. Armaroli, V. Balzani, E. C. Constable and A. M. W. C. Thompson, *Inorg. Chem.*, 1995, **34**, 2759.
- M. L. A. Abrahamsson, H. B. Baudin, A. Tran, C. Philouze, K. E. Berg, M. K. Raymond-Johansson, L. C. Sun, B. Akermark, S. Styring and L. Hammarström, *Inorg. Chem.*, 2002, **41**, 1534.
- Y. H. Xu, G. Eilers, M. Borgstrom, J. X. Pan, M. Abrahamsson, A. Magnuson, R. Lomoth, J. Bergquist, T. Polivka, L. C. Sun, V. Sundström, S. Styring, L. Hammarström and B. Akermark, *Chem. – Eur. J.*, 2005, **11**, 7305.
- J. J. Snellenburg, S. P. Laptinok, R. Seger, K. M. Mullen and I. H. M. van Stokkum, *J. Stat. Softw.*, 2012, **49**, 1.
- A. Staniszewski, W. B. Heuer and G. J. Meyer, *Inorg. Chem.*, 2008, **47**, 7062.
- (a) P. Qu and G. J. Meyer, *Langmuir*, 2001, **17**, 6720–6728; (b) B. H. Farnum, J. J. Jou and G. J. Meyer, *Proc. Natl. Acad. Sci. U. S. A.*, 2012, **109**, 15628.